US ARMY RDECOM

U.S. Army Research, Development and Engineering Command

TECHNOLOGY DRIVEN. WARFIGHTER FOCUSED.

Transient Thermal Stability of Polymer Nanocomposites

Dr. Stephen Bartolucci, Dr. Jeffrey Warrender, Dr. Karen Supan
U.S. Army ARDEC – Benet Laboratories
DOD Multifunctional Materials for Defense 2012

Report Documentation Page

Form Approved
OMB No. 0704-0188

1. REPORT DATE	2. REPORT TYPE	3. DATES COVERED
AUG 2012		**00-00-2012 to 00-00-2012**

4. TITLE AND SUBTITLE	5a. CONTRACT NUMBER
Transient Thermal Stability of Polymer Nanocomposites	5b. GRANT NUMBER
	5c. PROGRAM ELEMENT NUMBER
6. AUTHOR(S)	5d. PROJECT NUMBER
	5e. TASK NUMBER
	5f. WORK UNIT NUMBER
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) **U.S. Army Research, Development and Engineering Command,Benet Laboratories,Watervliet Arsenal ,NY**	8. PERFORMING ORGANIZATION REPORT NUMBER
9. SPONSORING/MONITORING AGENCY NAME(S) AND ADDRESS(ES)	10. SPONSOR/MONITOR'S ACRONYM(S)
	11. SPONSOR/MONITOR'S REPORT NUMBER(S)

12. DISTRIBUTION/AVAILABILITY STATEMENT
Approved for public release; distribution unlimited

13. SUPPLEMENTARY NOTES
Presented at the 2nd Multifunctional Materials for Defense Workshop in conjunction with the 2012 Annual Grantees'/Contractors' Meeting for AFOSR Program on Mechanics of Multifunctional Materials & Microsystems Held 30 July - 3 August 2012 in Arlington, VA. Sponsored by AFRL, AFOSR, ARO, NRL, ONR, and ARL.

14. ABSTRACT

15. SUBJECT TERMS

16. SECURITY CLASSIFICATION OF:			17. LIMITATION OF ABSTRACT	18. NUMBER OF PAGES	19a. NAME OF RESPONSIBLE PERSON
a. REPORT **unclassified**	b. ABSTRACT **unclassified**	c. THIS PAGE **unclassified**	**Same as Report (SAR)**	**23**	

Motivation

Composites

Weapon Systems/Components

Energy Transduction



Motivation

Nanocomposite properties

- Lightweight
- Inexpensive
- Processible
- Good mechanical properties

DoD applications

- Weapon systems
- Components
- Munitions
- High-frequency high-voltage switching

Bridging this gap requires understanding the kinetics of degradation under transient thermal loading

Transient Heating

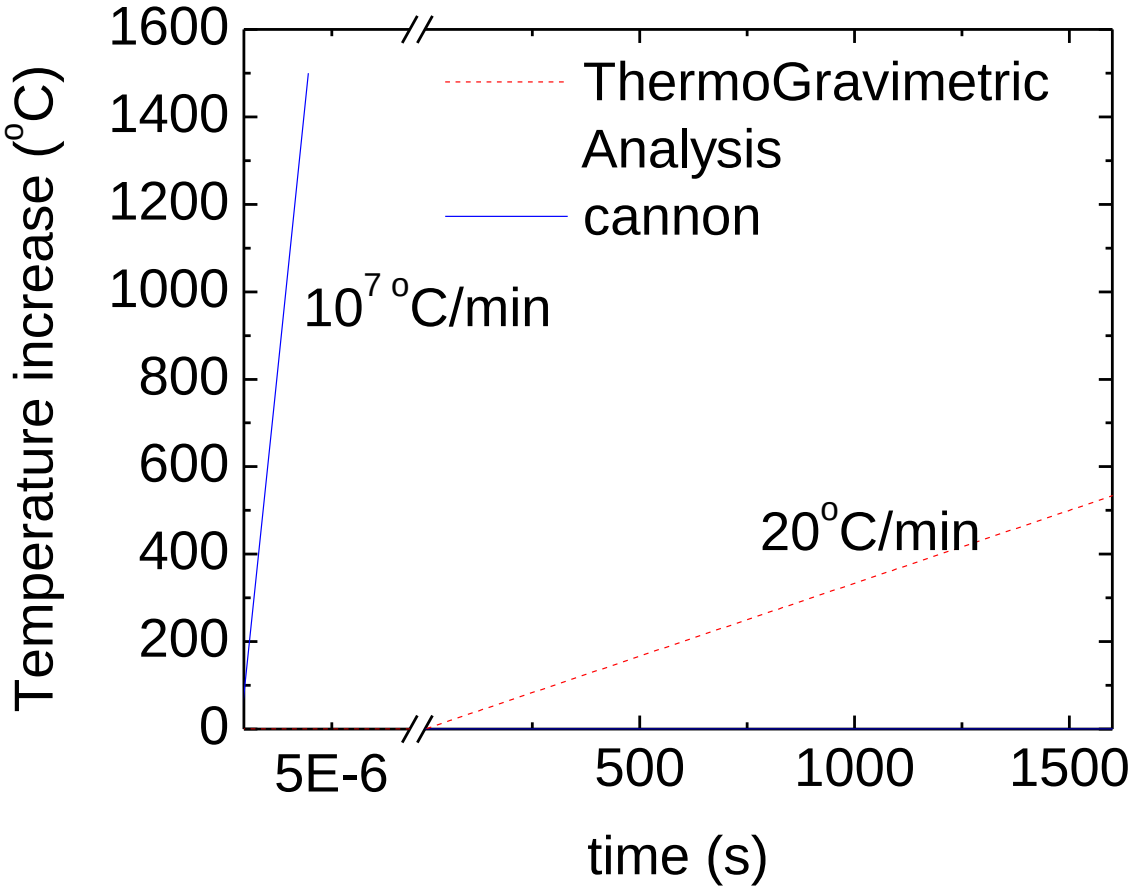

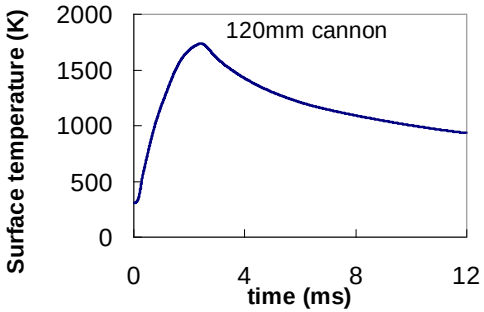

Six orders of magnitude difference in heating rate

Goal of this project

Use polypropylene as a model system to investigate degradation kinetics during transient heating

Materials



Isotactic Polypropylene

+

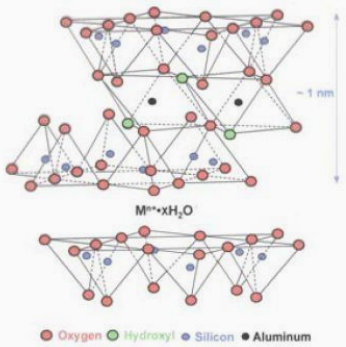

0-50 wt % nanoclay (modified Montmorillonite, Nanocor masterbatch)

(Na,Ca)0.33(Al,Mg)2(Si4O10)(OH)2·*n*H2O

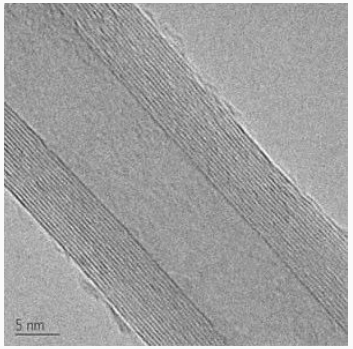

Multiwalled Carbon Nanotubes (Nanocyl masterbatch)

1 wt % carbon black

Twin screw extrusion (190C)

Slow Heating Regime

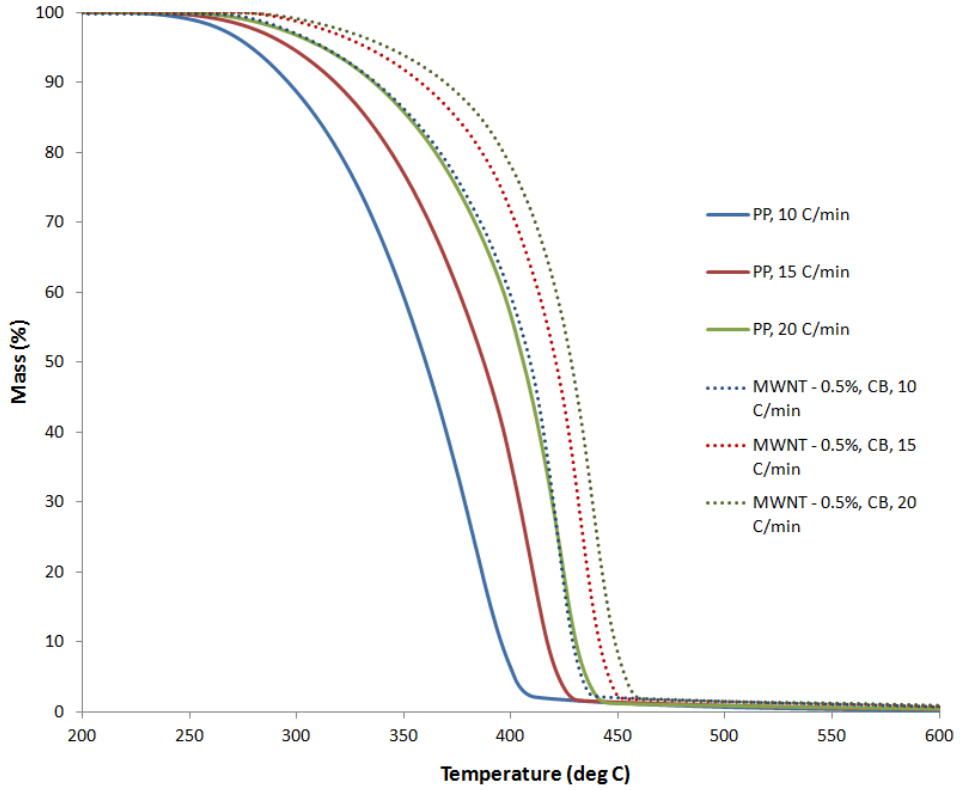

Thermogravimetric Analysis

Nanospecies improve thermal stability as expected

Laser pulse heating

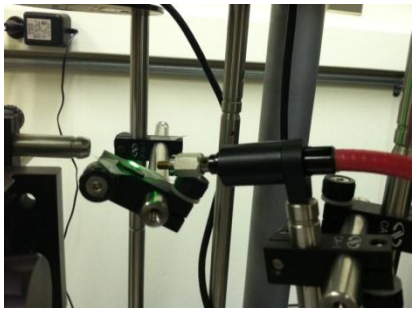

$$\ln(n_p\lambda^4) = \ln A - \frac{1}{T}\frac{hc}{k\lambda}$$

Laser pulse heating

Photothermal processes

⟶ Thermal decomposition

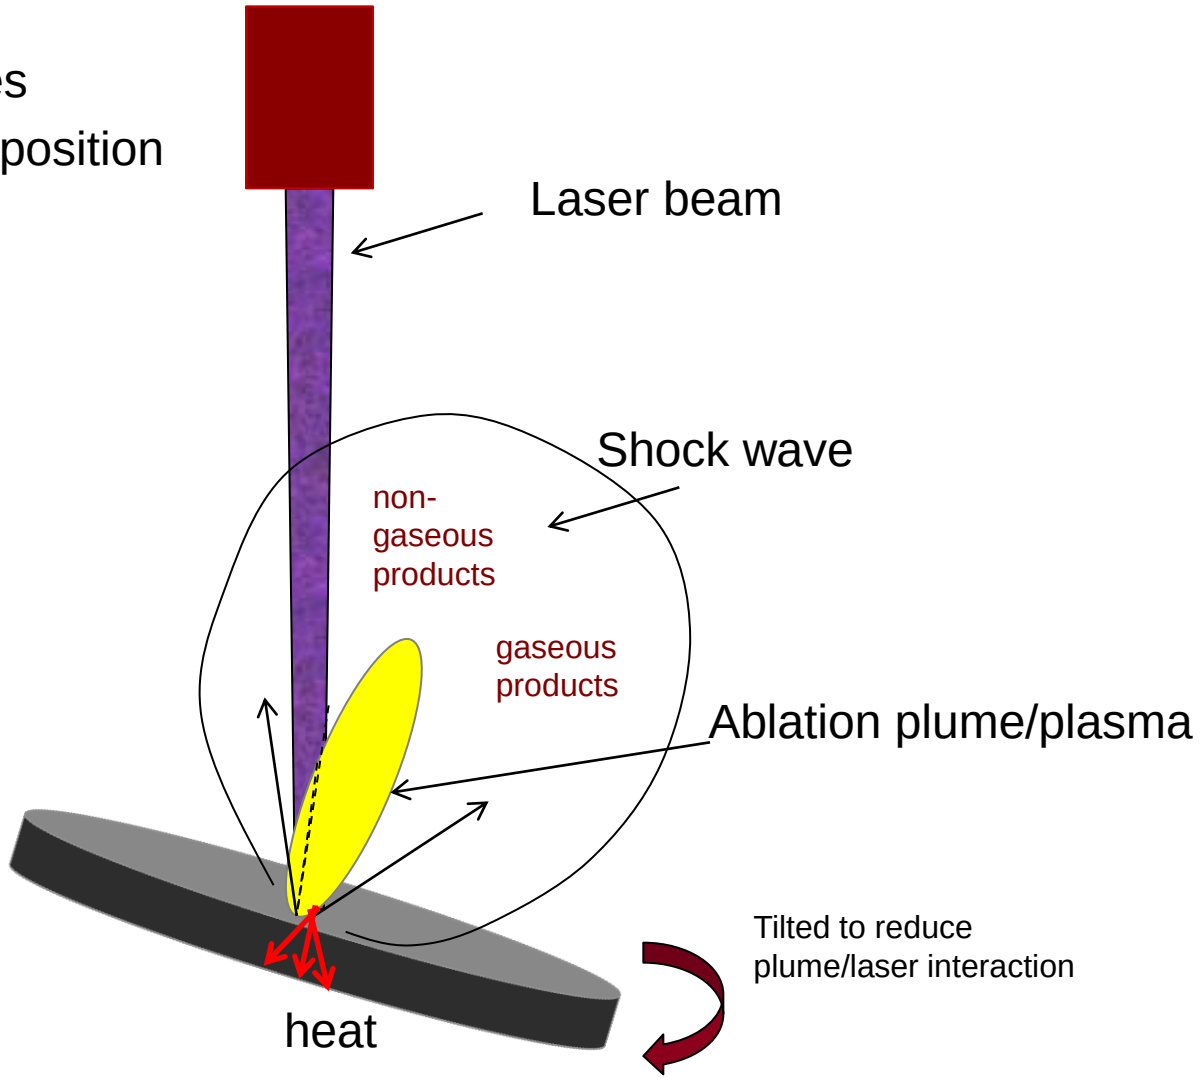

Real-time monitoring of irradiation

High Speed Videos

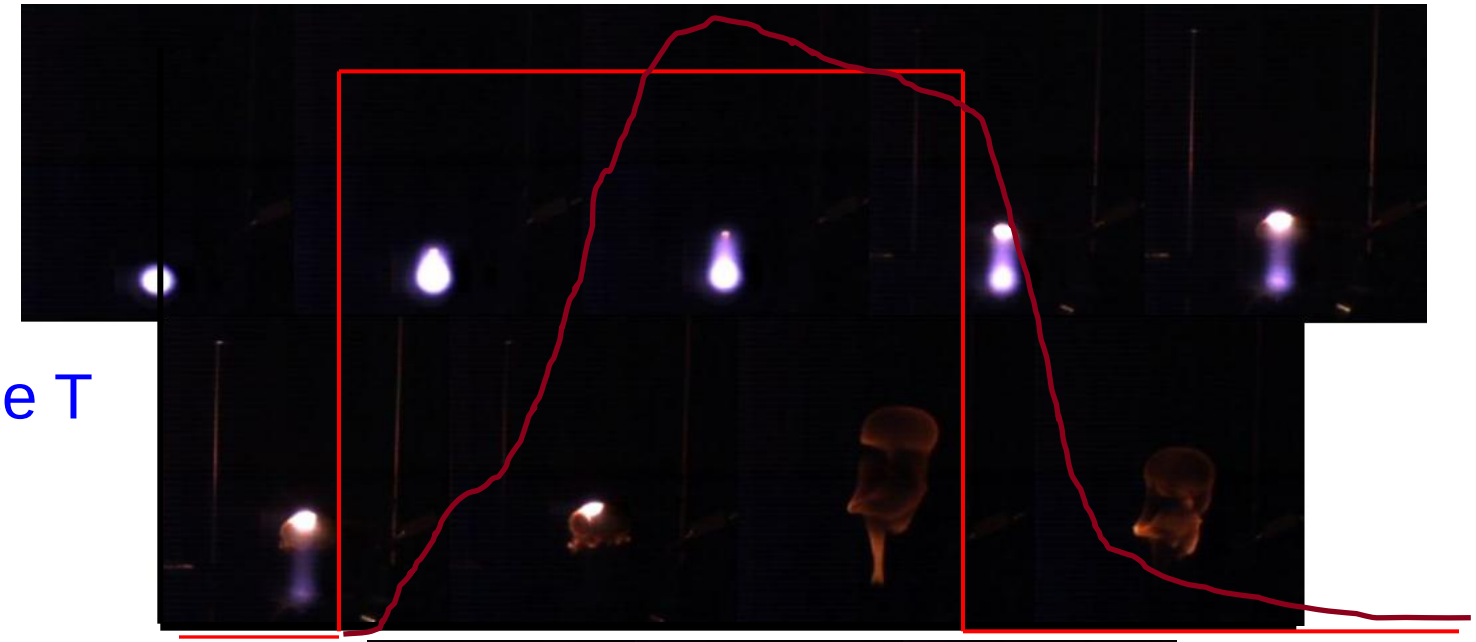

Surface T cools

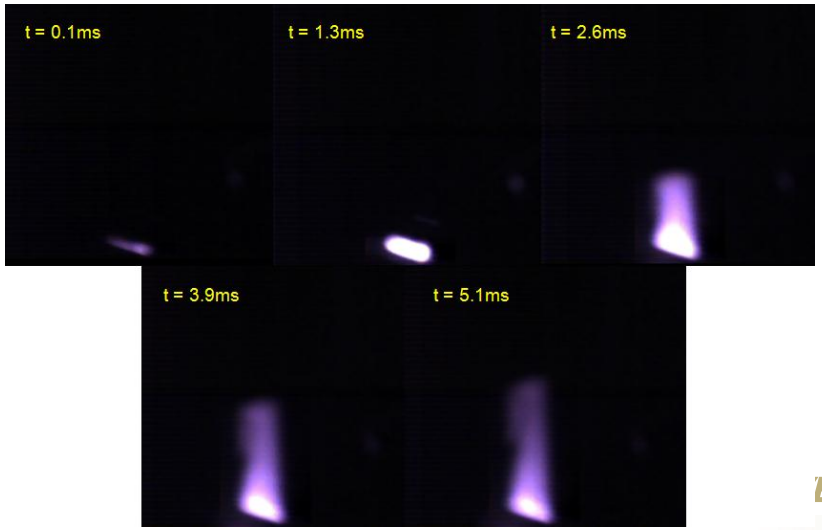

Surface T plateau

Thermogravimetric Analysis

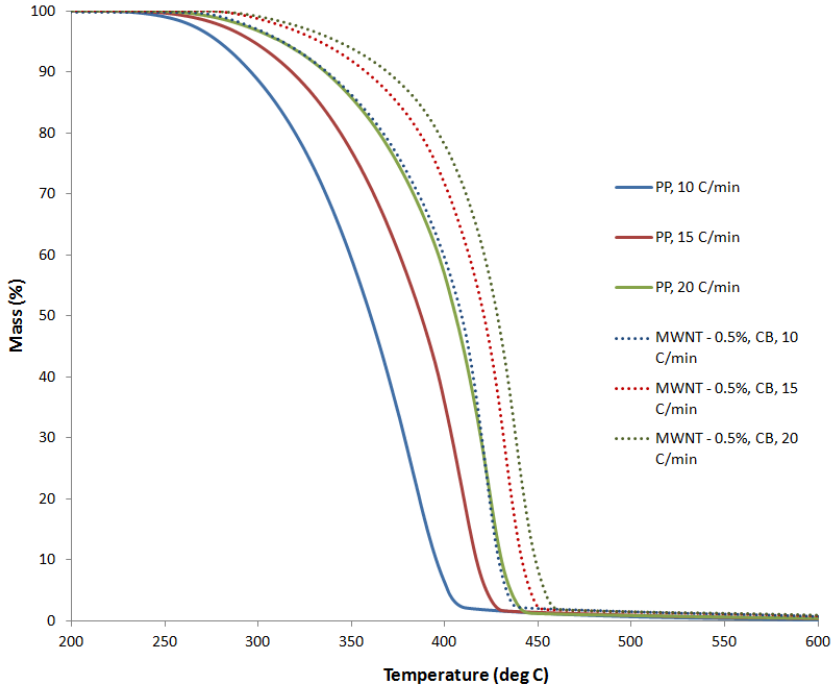

$$\frac{dC}{dT} = \frac{A}{\beta} f(C) e^{-\frac{E}{RT}}$$

Obtain activation energy

Temperature Measurements

1. Measure emitted photopower at varying λ

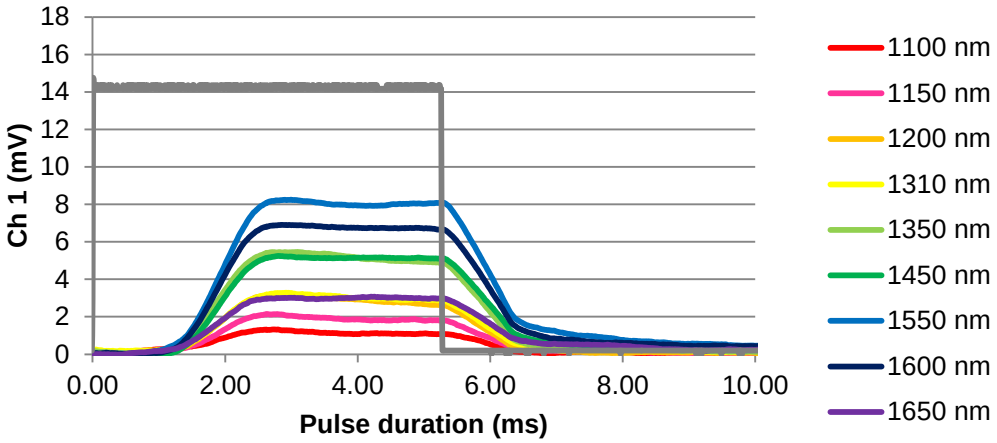

Temperature Measurements

1. Measure emitted photopower at varying λ

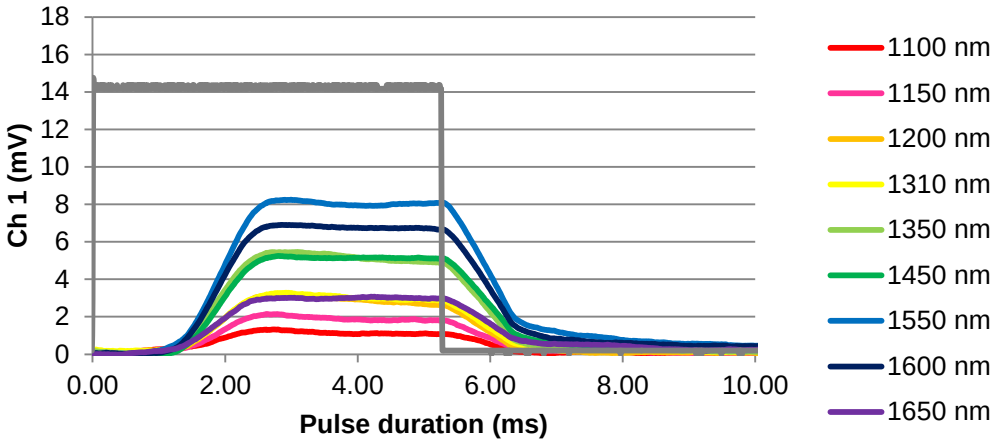

2. Fit to Planck's Law at each time step

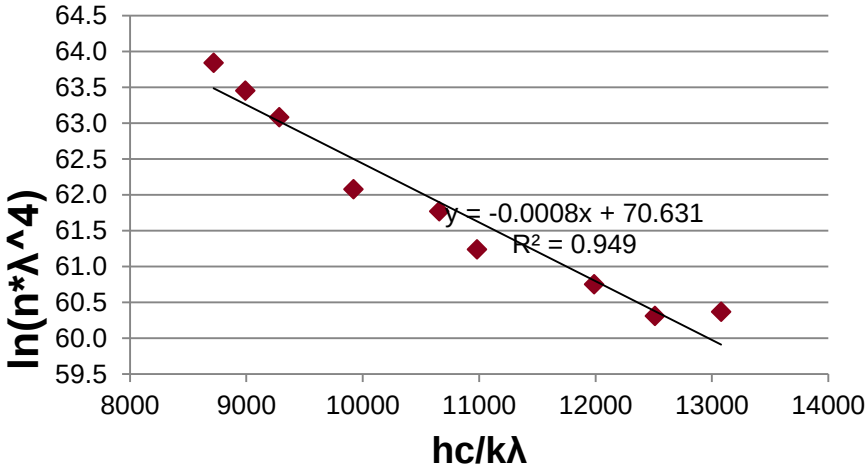

Temperature Measurements

1. Measure emitted photopower at varying λ

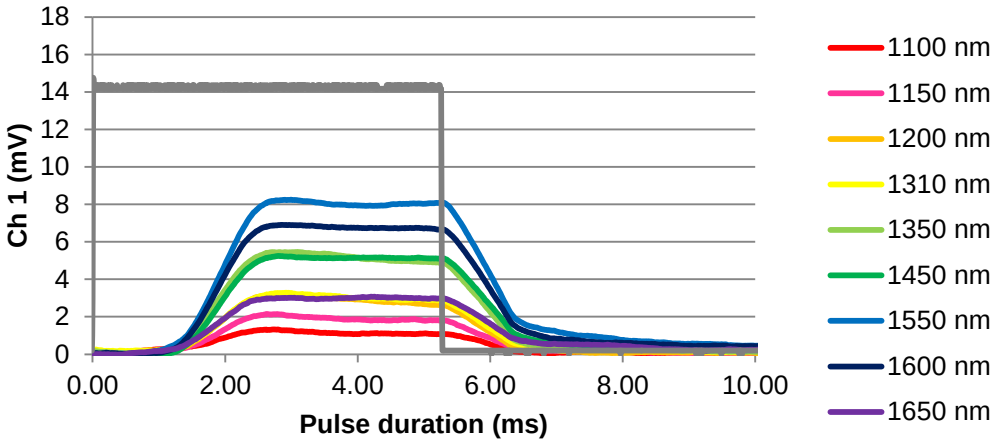

2. Fit to Planck's Law at each time step

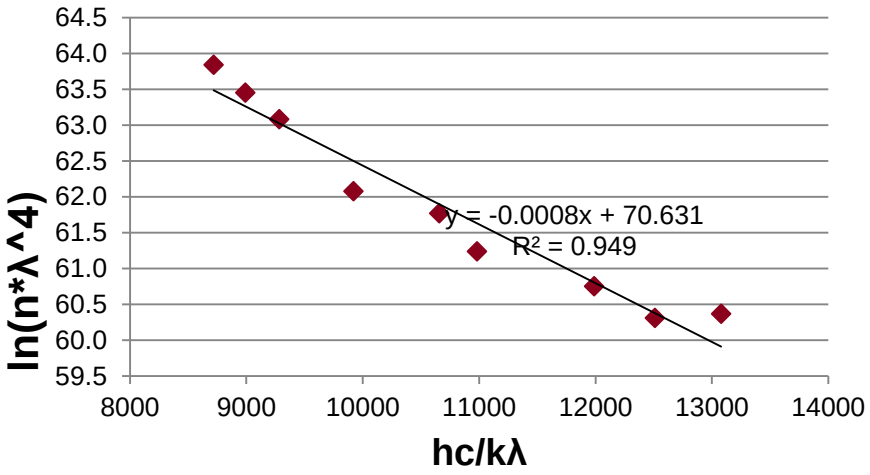

3. Calculate temperature

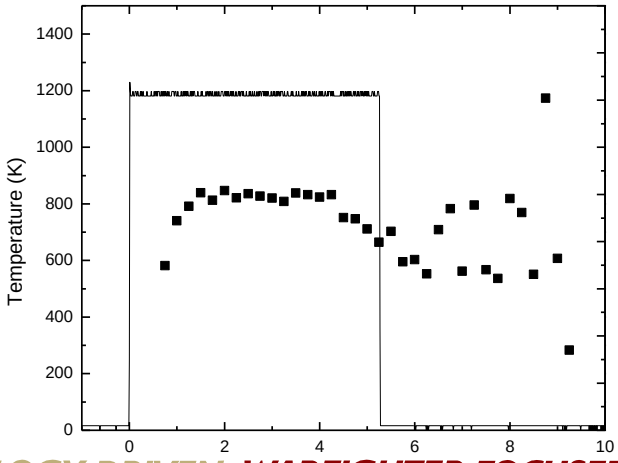

Mass change

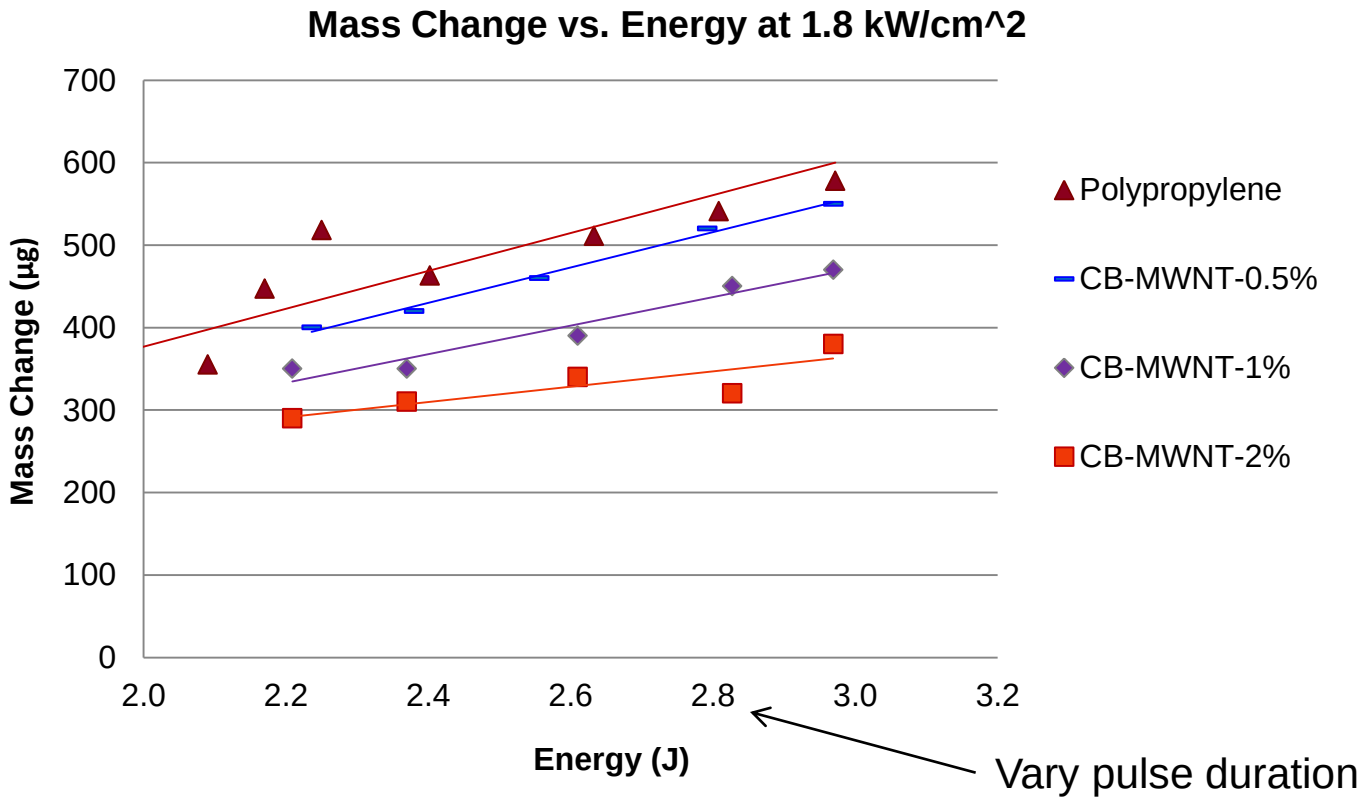

- Nano-Clay and Nanotubes decrease mass loss during LPH

Real-time mass measurement

Nd:YAG Laser

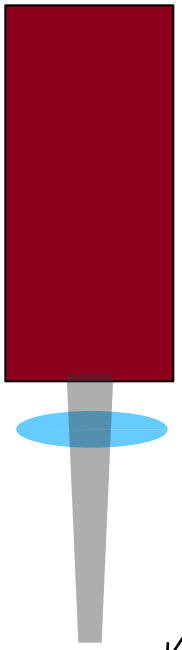

Sample

Quartz crystal

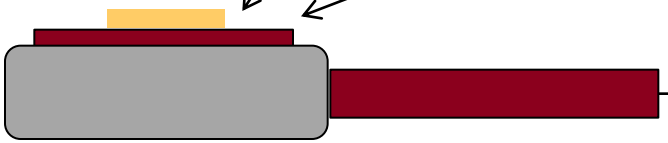

Quartz Crystal Microbalance

Quartz Crystal with Polymer Film and Laser Spot

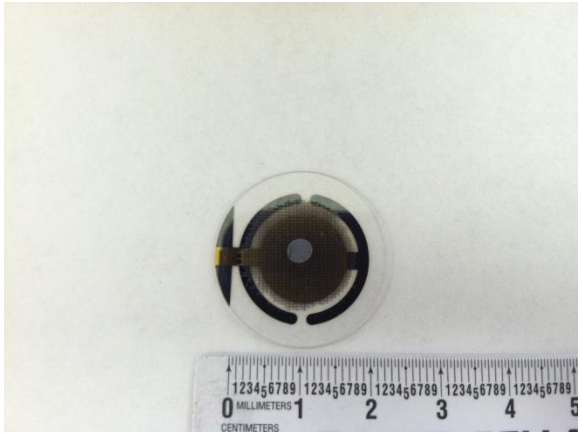

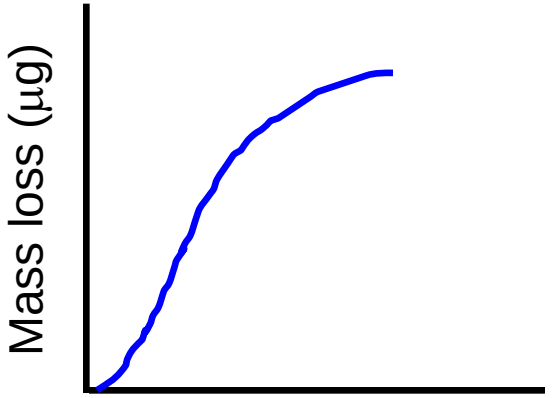

Frequency Counter

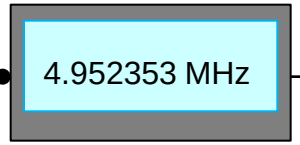

Data recording
And calibration
program

Mass change vs. clay content

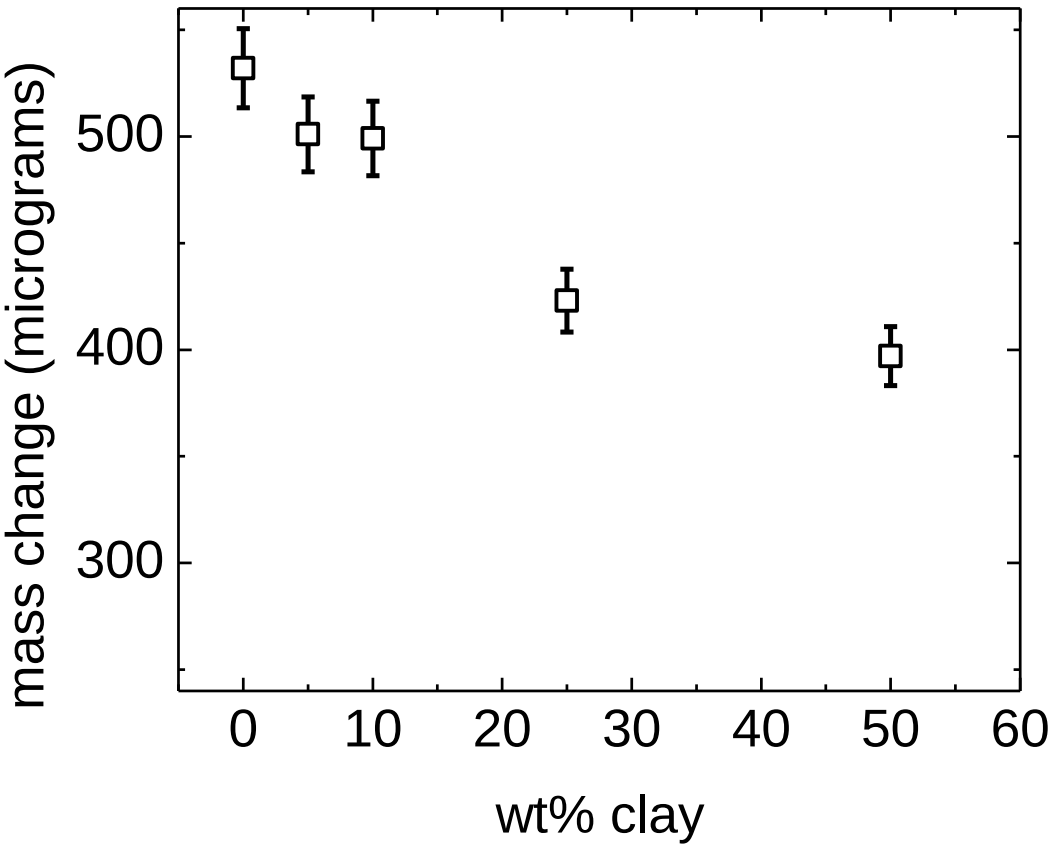

The mass change after a 10 ms shot is reduced as clay content increases

FE-SEM

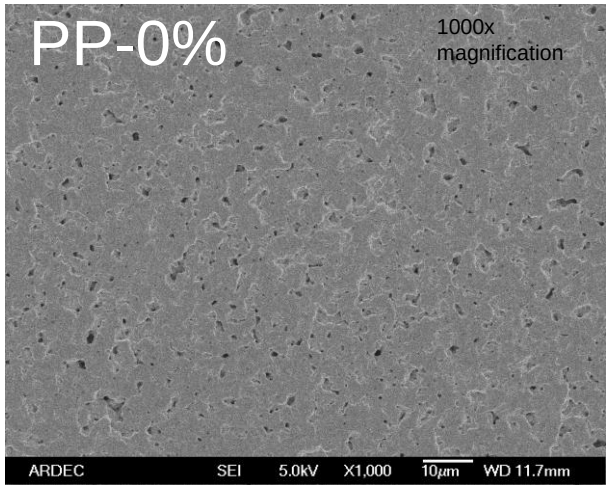

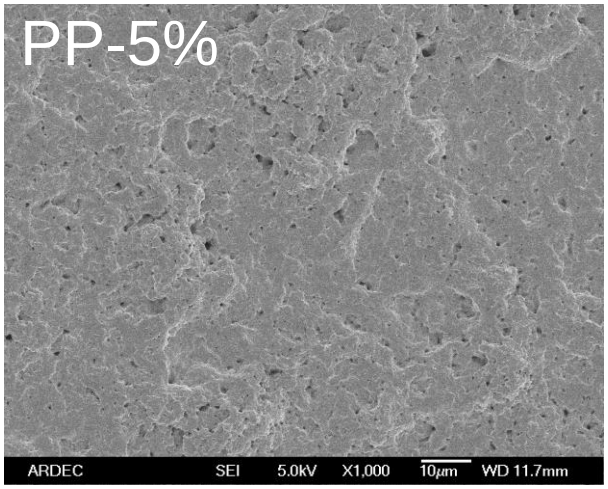

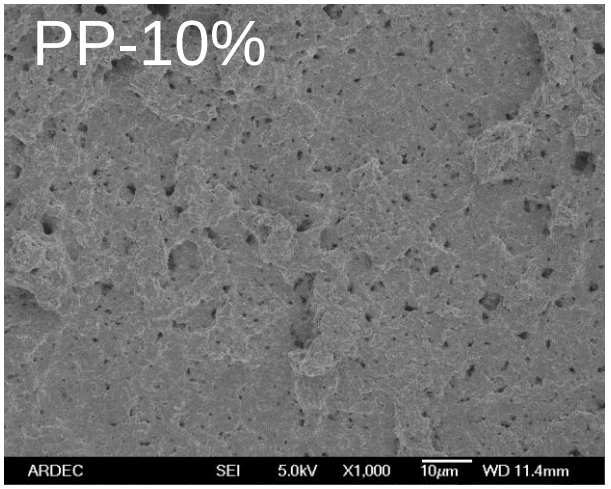

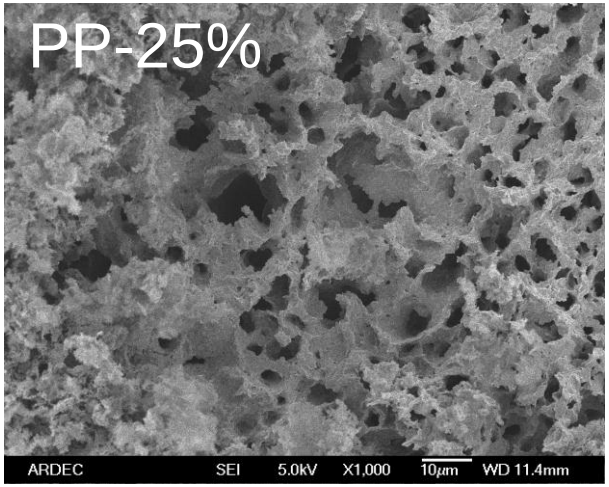

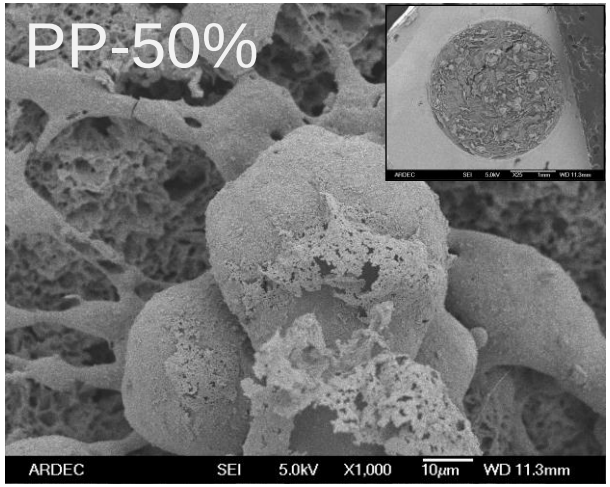

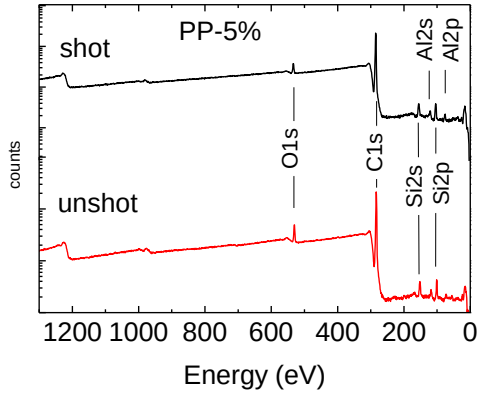

Smooth surface: lower threshold fluence, higher ablation rate and increased gaseous decomposition products seen in polymer ablation *Lippert, 2003, Chem. Rev.

Chemical changes

- We are looking at chemical changes before and after LPH
- TGA-Mass Spectrometry (LPH-MS goal)

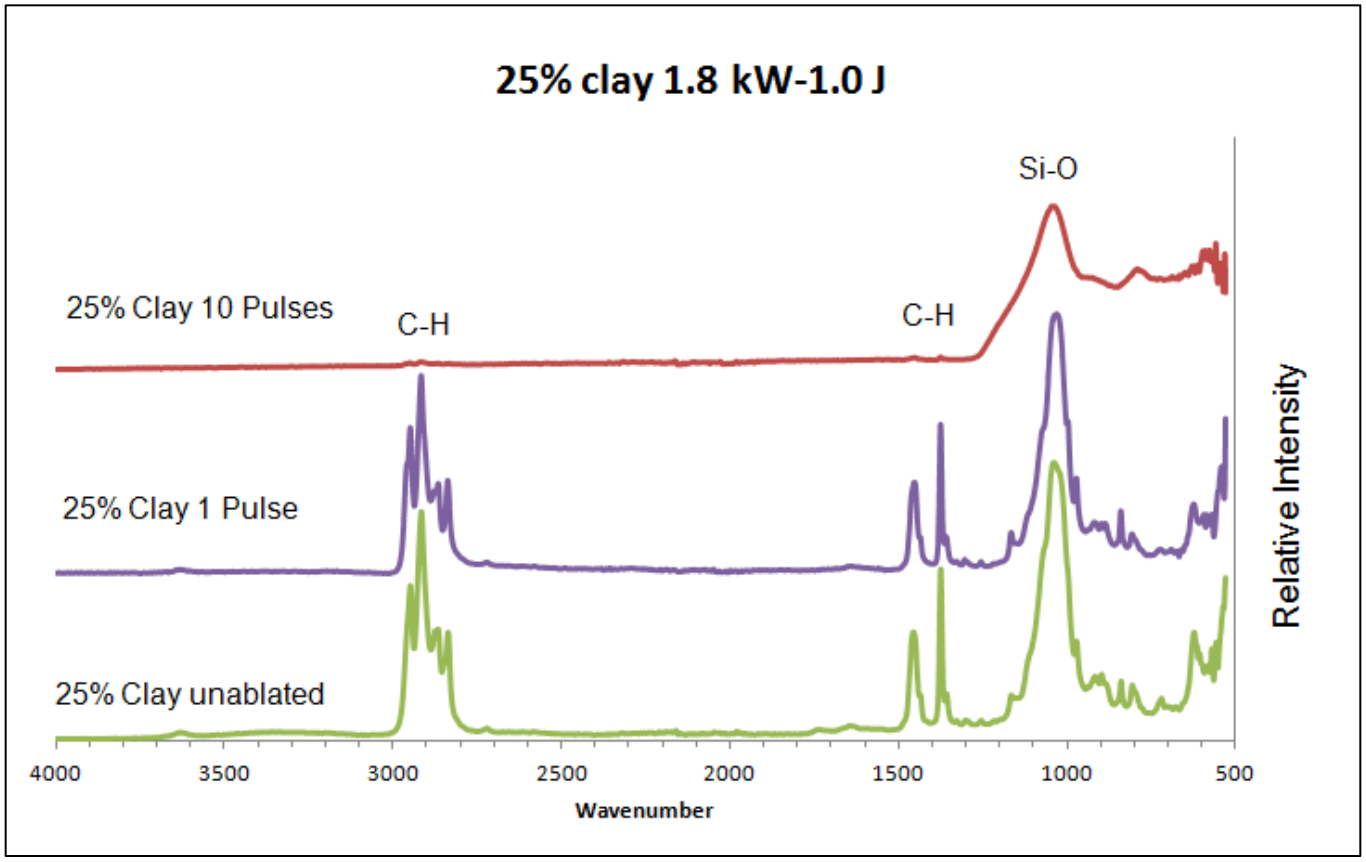

FTIR of clay nanocomposites

Polymer ablated
(loss of C-H bonds)

Clay/Oxides remain
on surface

Multi-Pulse Behavior

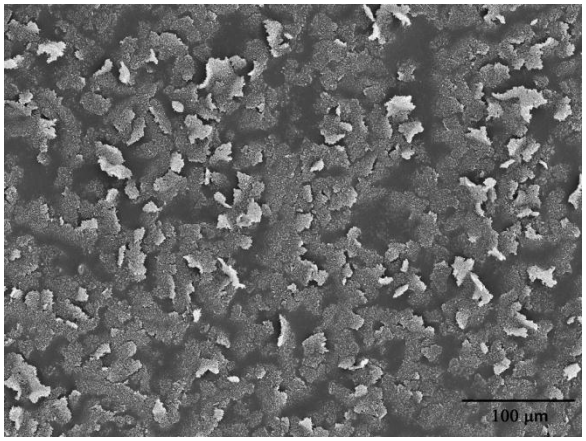

PP

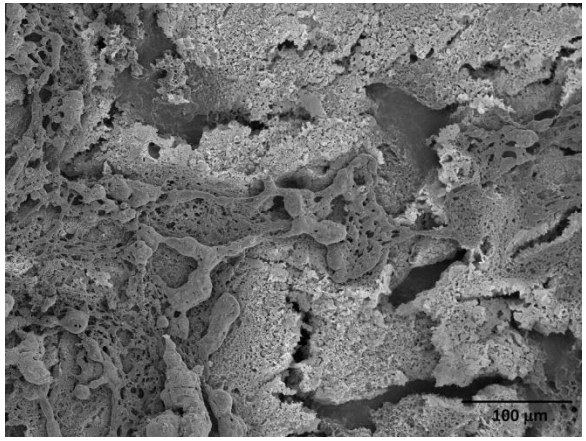

PP-25wt% nanoclay

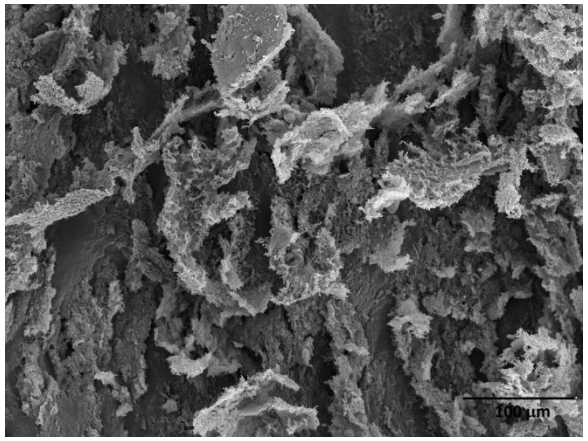

PP-2wt%MWNT

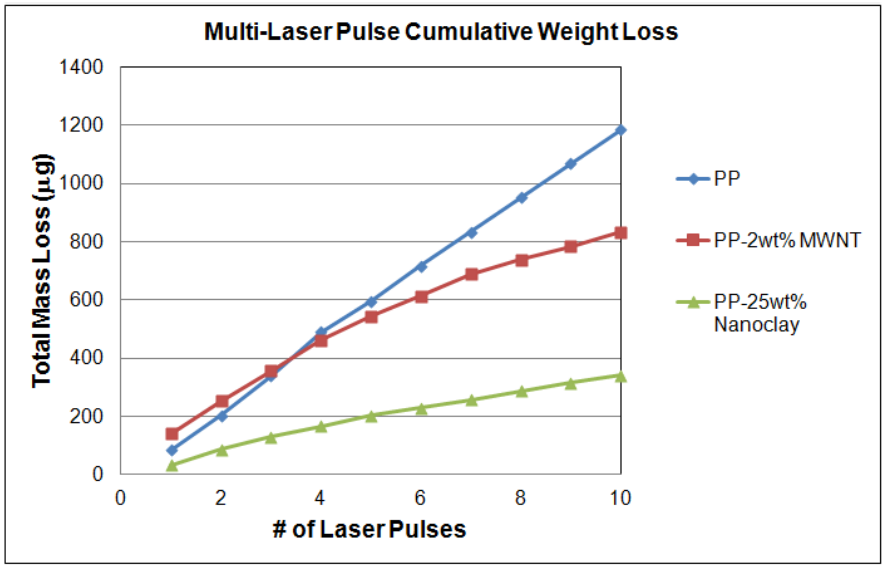

$$X=(2Dt)^{0.5}$$

 # α t

Becomes a diffusion limited Problem.

heat **mass**

Multi-Pulse Behavior

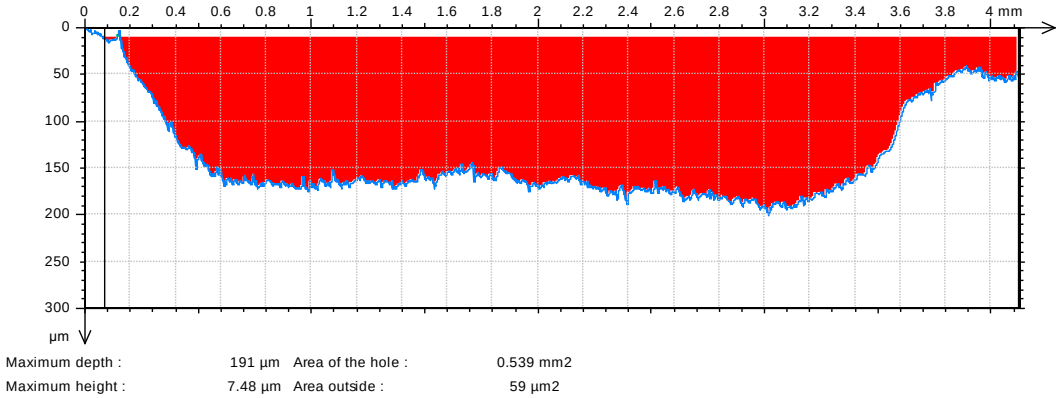

Maximum depth : 191 µm Area of the hole : 0.539 mm2
Maximum height : 7.48 µm Area outside : 59 µm2

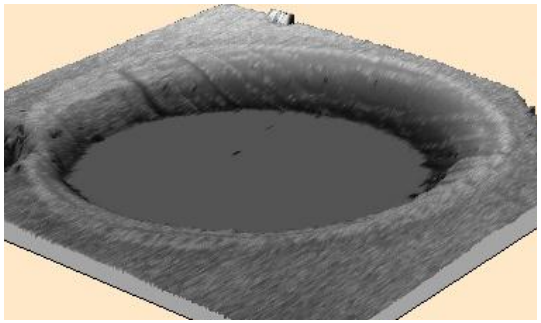

PP

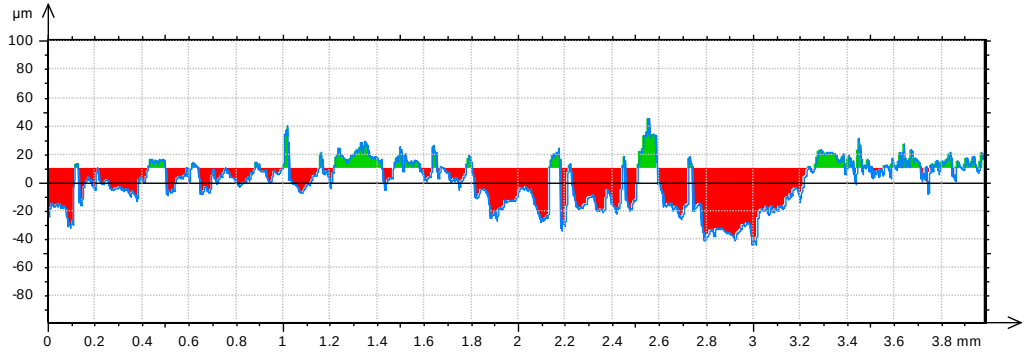

Maximum depth : 53.9 µm Area of the hole : 48758 µm2
Maximum height : 35.5 µm Area outside : 9557 µm2

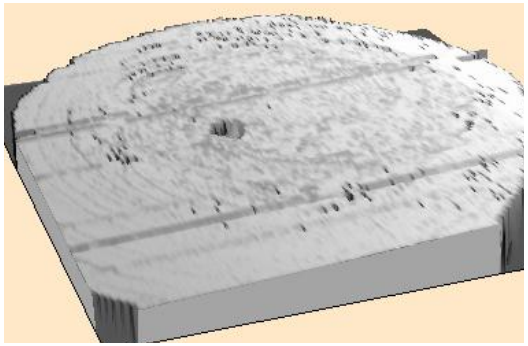

25% clay

Summary

- Research the behavior of polymer nanocomposites during LPH
- Temperatures exceed melting point and degradation temp of base polymer
- Nanoclay and Nanotubes provide degradation resistance
- Novel TGA-LPH technique being developed

Acknowledgements

- **US Army Benet Labs**
  - Dr. Karen Supan – NRC Post-doc
  - Student hires – Christopher Davis (MIT), Sara Duenas-Wolfson (Cornell)

- **University of Southern Mississippi**
  - Prof. Jeffery Wiggins
  - Lawrence La Beaud
  - Dr. Mohammad Hassan